



SCHULAMID[®] 6 GF 15 FR 4 K1681

Polyamide 6 Engineering Plastics

Product Description

15% glass fibre reinforced flame-retardant Polyamide 6 grade without PBDE

General

Material Status	• Commercial: Active		
Availability	• Africa & Middle East • Asia Pacific	• Europe • Latin America	• North America
Filler / Reinforcement	• Glass Fiber, 15% Filler by Weight		
Features	• Flame Retardant		
UL File Number	• E86615		
Processing Method	• Injection Molding		
Resin ID (ISO 1043)	• PA6 GF15 FR(17+30)		

Physical	Dry	Conditioned	Unit	Test Method
Density	1.38	--	g/cm ³	ISO 1183/A
Molding Shrinkage				ISO 294-4
Across Flow	0.80	--	%	
Flow	0.30	--	%	
Viscosity Number	145	--	cm ³ /g	ISO 307
Mechanical	Dry	Conditioned	Unit	Test Method
Tensile Modulus	1.03E+6 (7100)	580000 (4000)	psi (MPa)	ISO 527-2/1A/1
Tensile Stress (Break)	17000 (117)	10300 (71.0)	psi (MPa)	ISO 527-2/1A/5
Tensile Strain (Break)	3.5	8.5	%	ISO 527-2/1A/5
Impact	Dry	Conditioned	Unit	Test Method
Charpy Notched Impact Strength				ISO 179/1eA
-22°F (-30°C)	2.9 (6.0)	--	ft·lb/in ² (kJ/m ²)	
73°F (23°C)	3.3 (7.0)	6.7 (14)	ft·lb/in ² (kJ/m ²)	
Charpy Unnotched Impact Strength				ISO 179/1eU
-22°F (-30°C)	26 (55)	--	ft·lb/in ² (kJ/m ²)	
73°F (23°C)	29 (60)	33 (70)	ft·lb/in ² (kJ/m ²)	



SCHULAMID[®] 6 GF 15 FR 4 K1681

Polyamide 6
Engineering Plastics

Thermal	Dry	Conditioned	Unit	Test Method
Heat Deflection Temperature				
66 psi (0.45 MPa), Unannealed	433 (223)	--	°F (°C)	ISO 75-2/Bf
264 psi (1.8 MPa), Unannealed	397 (203)	--	°F (°C)	ISO 75-2/Af
Ball Pressure Test (392°F (200°C))	Pass	--		IEC 60695-10-2
RTI Elec				UL 746
0.015 in (0.38 mm)	266 (130)	--	°F (°C)	
0.030 in (0.75 mm)	266 (130)	--	°F (°C)	
0.06 in (1.5 mm)	266 (130)	--	°F (°C)	
0.12 in (3.0 mm)	266 (130)	--	°F (°C)	
RTI Imp				UL 746
0.015 in (0.38 mm)	167 (75.0)	--	°F (°C)	
0.030 in (0.75 mm)	194 (90.0)	--	°F (°C)	
0.06 in (1.5 mm)	212 (100)	--	°F (°C)	
0.12 in (3.0 mm)	212 (100)	--	°F (°C)	
RTI Str				UL 746
0.015 in (0.38 mm)	212 (100)	--	°F (°C)	
0.030 in (0.75 mm)	230 (110)	--	°F (°C)	
0.06 in (1.5 mm)	248 (120)	--	°F (°C)	
0.12 in (3.0 mm)	248 (120)	--	°F (°C)	
Electrical	Dry	Conditioned	Unit	Test Method
Surface Resistivity	> 1.0E+15	--	ohms	IEC 60093
Volume Resistivity	> 1.0E+13	> 1.0E+10	ohms-m	IEC 62631-3-1
Comparative Tracking Index	275	--	V	IEC 60112



SCHULAMID[®] 6 GF 15 FR 4 K1681

Polyamide 6
Engineering Plastics

Electrical	Dry	Conditioned	Unit	Test Method
High Amp Arc Ignition (HAI)				UL 746
0.015 in (0.38 mm)	PLC 0	--		
0.030 in (0.75 mm)	PLC 0	--		
0.06 in (1.5 mm)	PLC 0	--		
0.12 in (3.0 mm)	PLC 0	--		
Hot-wire Ignition (HWI)				UL 746
0.015 in (0.38 mm)	PLC 3	--		
0.030 in (0.75 mm)	PLC 0	--		
0.06 in (1.5 mm)	PLC 0	--		
0.12 in (3.0 mm)	PLC 0	--		
Flammability	Dry	Conditioned	Unit	Test Method
Burning Rate				ISO 3795
0.0150 in (0.380 mm), Self-Extinguishing	0.0	--	in/min (mm/min)	
0.0295 in (0.750 mm), Self-Extinguishing	0.0	--	in/min (mm/min)	
0.0591 in (1.50 mm), Self-Extinguishing	0.0	--	in/min (mm/min)	
0.118 in (3.00 mm), Self-Extinguishing	0.0	--	in/min (mm/min)	
Flame Rating				UL 94 IEC 60695-11-10, -20
0.015 in (0.38 mm)	V-2	--		
0.030 in (0.75 mm)	V-2	--		
0.06 in (1.5 mm)	V-2	--		
0.12 in (3.0 mm)	V-2	--		



SCHULAMID[®] 6 GF 15 FR 4 K1681


Polyamide 6
Engineering Plastics

Flammability	Dry	Conditioned	Unit	Test Method
Glow Wire Flammability Index				IEC 60695-2-12
0.015 in (0.38 mm)	1560 (850)	--	°F (°C)	
0.030 in (0.75 mm)	1760 (960)	--	°F (°C)	
0.06 in (1.5 mm)	1760 (960)	--	°F (°C)	
0.12 in (3.0 mm)	1760 (960)	--	°F (°C)	
Glow Wire Ignition Temperature				IEC 60695-2-13
0.015 in (0.38 mm)	1520 (825)	--	°F (°C)	
0.030 in (0.75 mm)	1650 (900)	--	°F (°C)	
0.06 in (1.5 mm)	1650 (900)	--	°F (°C)	
0.12 in (3.0 mm)	1650 (900)	--	°F (°C)	
Oxygen Index	26	--	%	ISO 4589-2



SCHULAMID[®] 6 GF 15 FR 4 K1681

Polyamide 6
Engineering Plastics

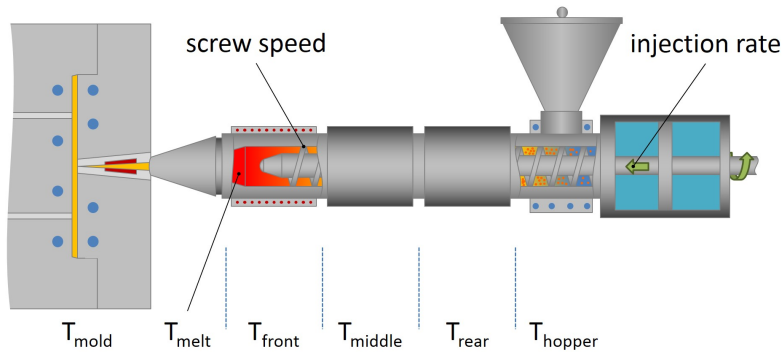

Injection	Dry (English)	Dry (SI)
Drying Temperature	176 °F	80 °C
Drying Time	4.0 to 6.0 hr	4.0 to 6.0 hr
Suggested Max Moisture	0.10 %	0.10 %
Suggested Max Regrind	25 %	25 %
Processing (Melt) Temp	446 to 464 °F	230 to 240 °C
Mold Temperature	140 to 194 °F	60 to 90 °C
Injection Rate	Slow-Moderate	Slow-Moderate
Back Pressure	290 to 1160 psi	2.00 to 8.00 MPa
Screw Speed	591 in/min	15 m/min

Injection Notes

Mould surface contacting melt should be of non-corrosive steel (content of chrome > 12%)